

Uniquely Engineered Electrodes and Wires Designed to Resist Severe Cavitation-Erosion Damage

CaviTec™



WELDING



SMA



GMA

- Extends the service life of hydro-turbine blades
- Reduces maintenance costs
- Available as stick electrode (SMA) or cored wire (GMA)
- Outlasts 308/309 stainless steel by up to six times
- High integrity weld deposits
- Free from micro-cracking
- Readily profiled and contoured

Castolin Eutectic®
Eutectic Castolin

DESCRIPTION:

A patented, proprietary alloy uniquely engineered to resist damage from severe cavitation-erosion, CaviTec is manufactured under license from Hydro-Quebec-Canada. CaviTec, with its enhanced properties, is an austenitic-type alloy containing controlled amounts of chromium, cobalt, silicon and manganese. The finely controlled balance of these elements significantly improves strain-hardening and shock-dampening properties. The result: improved cavitation-erosion resistance.

CaviTec is proven to last up to six times longer than traditional stainless steel overlays. This high strain, work-hardening austenitic stainless steel delivers maximum protection for areas needing frequent or major repairs. CaviTec's all position weldability also makes controlled overlapping and profiling very easy to do.

Essentially an austenitic γ -phase structure. This metastable phase transforms under cyclical stress to an α -martensitic phase which results in a very fine deformation twinning.

TYPICAL APPLICATIONS:

For use on...

- Francis turbines
- Kaplan turbines
- Propeller turbines
- Bulb turbines
- Draft tubes
- Impellers
- Pumps & valves
- Wicket gates

TECHNICAL DATA:

SMA and GMA

Typical Hardness (HV ₅₀)	250-280 - As deposited 270-300 - A27 plain carbon Steel 230-260 - 308/309 stainless steel
Typical Work (HV ₅₀)	400-450- Work hardened
Polarity	DCEP(+)

RECOMMENDED WELDING PROCEDURE*:

Preparation: Remove damaged area with arc-air or plasma gouging. Grind gouged surface to remove oxides and slag. Minimum depth of preparation should be 1/8". If the refill depth is greater than 3/8" first fill with a grade 308 or 309 or the "L" version. This preparation is needed to maintain a maximum CaviTec deposit depth of 3/8".


Technique: Maintain a medium-to-short arc and incline the electrode at a 45° angle in the direction of travel. The preferred bead profile should be a non-weave. Back-fill craters to reduce crater-cracking tendencies.

Parameters: Please contact Eutectic's Technical Services for application welding parameters.

Post-welding: Grind to profile

(* In highly stressed regions of the turbine runner it is recommended that a buttering layer of 309L be deposited. In such cases, the minimum depth of preparation should be increased to 1/4" (6mm).)

RELATIVE CAVITATION-EROSION RESISTANCE

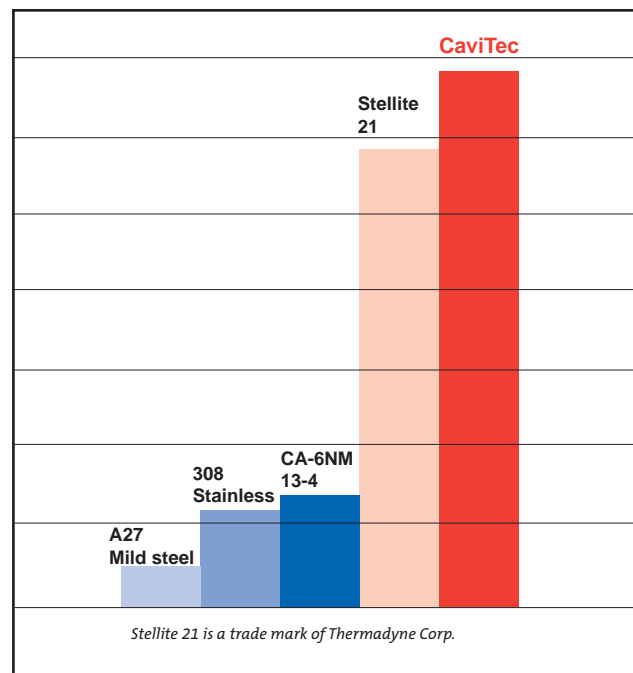

YOUR RESOURCE FOR PROTECTION, REPAIR AND JOINING SOLUTIONS



EUTECTIC CORPORATION
N94 W14355 Garwin Mace Drive
Menomonee Falls, WI 53051 USA
Tel.: +1 (800) 558-8524
eutectic.com

EUTECTIC CANADA
428, rue Aimé-Vincent
Vaudreuil-Dorion, Québec
J7V 5V5 Canada
Tel.: +1 (800) 361-9439
eutectic.ca

