




Atomized Nickel-Based Alloy
Recommended for Use with
Thermal Spray Equipment

Eutectic®

13495

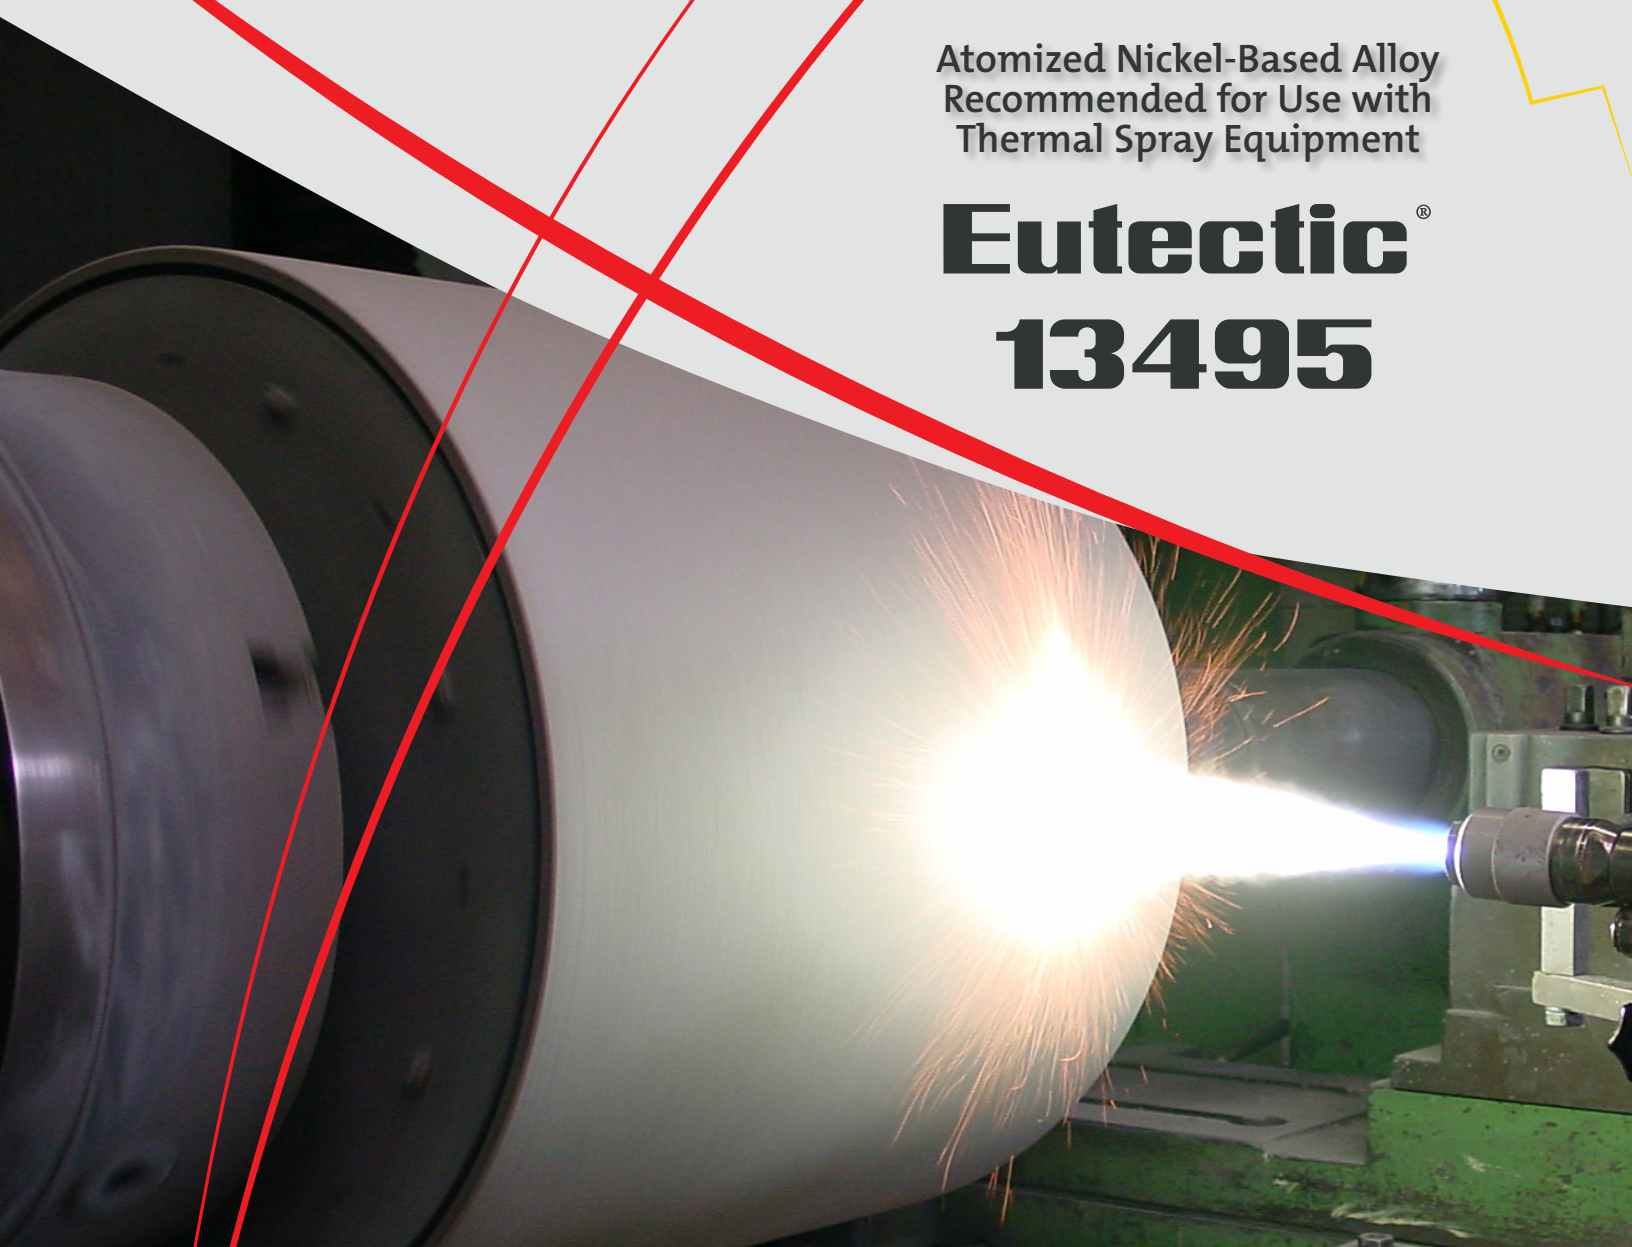

- Precise particle sizing ensures consistent deposition, fusing and hardness
- Exceptionally hard deposits have high resistance to abrasion and friction
- May be used in a wide variety of thermal spray processes

TECHNICAL DATA

Eutectic® 13495

Eutectic 13495 is a high performance atomized nickel alloy powder optimized to produce hard, durable, abrasion, and friction resistant coatings with a multitude of thermal spray process equipment. Controlled composition based on AWS A5.13 and precise particle sizing ensures consistent deposition, fusing and hardness.

Typical Powder Properties	
Melting Range:	Solidus: 1760°F (960°C)
	Liquidus: 2000°F (1093°C)
	Furnace Fusing: 2170°F (1188°C)(Set Point)
Hall Flow Rate:	18 seconds
Bulk Density:	4.0 g/cc
Powder Coverage:	0.042 lbs/ft² @ 0.001"

Typical Coating Properties	
Marco Hardness:	49 HRC
Shrinkage on Fusing:	17-20%
Density:	7.6 g/cc

PROCEDURE FOR USE

Grinding Wheel Type: Green Silicon Carbide
 Grit Size: 60 - 80
 Grade: H (soft)
 Structure: 5
 Bond Type: Vitriified
 Wheel Speed: Use Manufacturer's Recommendation
 Work Speed: 50 -65 surface feet per minute
 Coolant: Flood coolant with rust inhibitors in 2-5% concentration

	Traverse Speed	In-Feed
Roughing	5-15 inches per minute	0.001 inches per pass
Finishing	3-8 inches per minute	0.0005 inches per pass or less

Notes: 1. Before grinding, all edges and ends of coating must be chamfer ground.
 2. Frequently dress the grinding wheel face to reduce friction and heat.

TD 2000

Nozzle: RL 200
 RotoJet: RPA 3 @ 15 psi air
 Module Adaptor: Yellow/Red Multi-Oriface set to 3
 Oxygen: 50 psi / 30 flow (FM-1 flowmeter)
 Acetylene: 12 psi / 60 flow (FM-1 flowmeter)
 Coating Rate: 24.0 lb/hr
 Deposit Efficiency: 90%
 Spray Distance: 6 to 8 inches
 T-Valve: 20 clicks

TD 3000

Nozzle: RL 200
 Oxygen: 50 psi / 32 flow
 Acetylene: 12 psi / 48 flow
 Carrier Gas: Nitrogen @ 55 psi
 Terometer: 130
 Coating Rate: 20 lb/hr
 Deposit Efficiency: 90%
 Spray Distance: 6 to 8 inches

TYPICAL APPLICATIONS

- Wash pipes (petroleum drilling)
- Guide plates
- Trimming dies
- Auger flights
- Pistons
- Hydraulic cylinders

Observe normal spraying practices, respiratory protection and proper air flow pattern advised. For general spray practices, see AWS Publications AWS C2.1-73, "Recommended Safe Practices for Thermal Spraying and AWS TSS-85, "Thermal Spraying, Practice, Theory and Application." Thermal spraying is a completely safe process when performed in accordance with proper safety measures. Become familiar with local safety regulations before starting spray operations. DO NOT operate your spraying equipment or use the spray material supplied, before you have thoroughly read the equipment instruction manual. Refer to the Eutectic website for Material Safety Data Sheet (MSDS) information. DISREGARDING THESE INSTRUCTIONS MAY BE HAZARDOUS TO YOUR HEALTH.



Eutectic Corporation:
 N94 W14355 Garwin Mace Dr.
 Menomonee Falls WI, 53051 USA
 +1 800. 558. 8524 • eutectic.com

Eutectic Canada:
 428, rue Aimé-Vincent Vaudreuil-Dorion,
 Québec J7V 5V5 Canada
 +1 800. 361. 9439 • eutectic.ca



Follow Us On...

